



# Elastic Modulus by Resonance of Rectangular Prisms: Corrections for Edge Treatments

by George D. Quinn  
and Jeffrey J. Swab

ARL-TN-165

July 2000

Approved for public release; distribution is unlimited.

20000831 054

DTIC QUALITY INSPECTED 4

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

Citation of manufacturer's or trade names does not constitute an official endorsement or approval of the use thereof.

Destroy this report when it is no longer needed. Do not return it to the originator.

---

---

## Abstract

---

The dynamic elastic moduli of isotropic, homogeneous ceramics is commonly determined by resonance methods. A prismatic beam specimen is vibrated in a flexural mode, and the resonant frequency is measured. The beam may have a square, rectangular, or circular cross section. Elastic modulus is determined from the resonant frequency, the mass or density of the prism, and the beam's physical dimensions. Under ideal circumstances, the beam cross section should have a simple prismatic shape, but in practice, the method is sometimes applied to rectangular specimens with edge chamfers or radii that are applied to reduce edge flaw sensitivity during strength tests. The effect of such edge treatments on the resonance frequency and a simple means to correct the calculated elastic modulus for the edge treatment are provided in this note.

# Table of Contents

	<u>Page</u>
List of Figures .....	v
List of Tables .....	v
1. Introduction .....	1
2. Experimental Procedure .....	8
3. Results and Discussion .....	10
4. Summary .....	12
5. References .....	13
Distribution List .....	15
Report Documentation .....	19

INTENTIONALLY LEFT BLANK.

## List of Figures

<u>Figure</u>	<u>Page</u>
1. Specimen Cross Section for a Chamfered-Edge Beam.....	4
2. Specimen Cross Section for a Rounded-Edge Beam .....	4

## List of Tables

<u>Table</u>	<u>Page</u>
1. Correction Factors, F and P, for Chamfered Standard 3-mm $\times$ 4-mm Strength Test Specimens .....	6
2. Correction Factors, F and P, for Edge-Rounded Standard 3-mm $\times$ 4-mm Strength Test Specimens .....	7
3. $E_{b,m}$ and $E_{cor}$ Values for Ceramic Materials.....	9
4. Comparison of Corrected Beam Resonance Elastic Moduli, $E_{cor}$ , to Values From Other Methods .....	11

INTENTIONALLY LEFT BLANK.

# 1. Introduction

The dynamic elastic moduli of isotropic, homogeneous ceramics is commonly determined by resonance methods [1–6]. A prismatic beam specimen is vibrated in a flexural mode, and the resonant frequency is measured. The vibration may either be by continuous or impulse excitation. The beam may have a square, rectangular, or circular cross section. Elastic modulus is determined from the resonant frequency, the mass or density of the prism, and the beam's physical dimensions. Under ideal circumstances, the beam cross section should have a simple prismatic shape, but in practice, the method is sometimes applied to rectangular specimens with edge chamfers or radii that are applied to reduce edge flaw sensitivity during strength tests. The effect of such edge treatments on the resonance frequency and a simple means to correct the calculated elastic modulus for the edge treatment are provided in this note.

The basic wave equation for the propagation of an elastic wave in an elastic medium is

$$E = \rho v^2, \quad (1)$$

where  $E$  is the elastic modulus,  $\rho$  is the material density, and  $v$  is the wave speed. Goens [7] solved Timoshenko's [8] equation relating Young's modulus to the flexural resonance frequency for bars of different cross section. Pickett [3] further simplified Goen's solution for elastic modulus,  $E$ , which may be expressed in the following form:

$$E = C_1 W f^2, \quad (2)$$

where  $W$  is weight of the prism,  $f$  is the flexural resonant frequency, and  $C_1$  is given by

$$C_1 = \frac{4\pi^2 \ell^3 T_1}{gI(4.730)^4}, \quad (3)$$



where  $\ell$  is the prism length,  $g$  is the gravitational constant,  $I$  is the second moment of inertia for the beam cross section, and  $T_1$  is a dimensionless geometric constant that depends upon the radius of gyration of the prism cross section, the length of the prism, and Poisson's ratio. Subsequent analysis and experimental work [1, 2, 4, 5] refined the equations for  $T_1$  and led to an equation for  $E$ :

$$E_{b,\rho} = 0.9465 \frac{\rho \ell^4 f^2}{d^2} T, \quad (4)$$

where  $d$  is the specimen thickness and  $T$  is a new dimensionless geometric term. The subscripts  $b$  and  $\rho$  attached to  $E$  denote the formula is for an ideal rectangular beam (no edge treatment) and the calculation uses the density.

For an ideal rectangular beam (no edge treatment)

$$\rho_b = m/(bd\ell), \quad (5)$$

where  $\rho_b$  is the material density,  $m$  is the mass, and  $b$  is the specimen width. Substituting into equation 4, results in

$$E_{b,m} = 0.9465 m f^2 \frac{T}{b} \left( \frac{\ell^3}{d^3} \right), \quad (6)$$

where the subscripts  $b$  and  $m$  attached to  $E$  denote that the formula calculates the modulus of an ideal rectangular beam (no edge treatment) using the mass and physical dimensions of the beam. This latter form is commonly used today in standard test methods.

Empirical solutions for  $T_1$  are available for ideal rectangular cross section prisms and are used in the ASTM flexural resonance standard test methods [9–14]. Several standards [9–12]

caution that chamfering or rounding of edges may create an experimental error of undefined magnitude. They recommend against the use of these bars, but this is unnecessarily restrictive as we will show.


The chamfers reduce the cross-sectional moment of inertia,  $I$ , and slightly alter the radius of gyration, and alter the relationship between density and the physical dimensions of the beam, equation 5. The effect upon  $I$  has previously been quantified in connection with work to minimize experimental error in flexure strength testing [15–17]. Even a small chamfer can alter  $I$  a meaningful amount and must be taken into account when preparing flexure specimens for strength testing. For example, a  $45^\circ$  chamfer of 0.15-mm size will reduce  $I$  by 1% for standard 3-mm  $\times$  4-mm cross section flexure strength specimens, which in turn causes the flexure stress to be underestimated by 1%. Consequently, the 0.15-mm chamfer size is the maximum allowed by several world flexure strength standards [18, 19]. Equations for  $I$ , for chamfered or round-edged beams in bending and error tables for the stress corrections, are available in the works of Baratta and coworkers [15, 16]. These equations for  $I$  are repeated here for convenience, and rather than list errors, a simple correction factor for the elastic modulus is furnished. The moment of inertia,  $I_b$ , for a rectangular cross section beam is

$$I_b = \frac{bd^3}{12}. \quad (7)$$


The true moment of inertia,  $I_t$ , for a beam with  $45^\circ$  chamfers of size  $c$ , as shown in Figure 1 [15, 16], is

$$I_t = \frac{bd^3}{12} - \frac{c^2}{9} \left( c^2 + \frac{1}{2} (3d - 2c)^2 \right), \quad (8)$$

where the second term on the right-hand side shows the reduction due to the chamfers. It is assumed that the four chamfers are identical in size. The true moment of inertia,  $I_t$ , for a beam with four identical rounded edges of radius  $r$ , as shown in Figure 2 [16], is

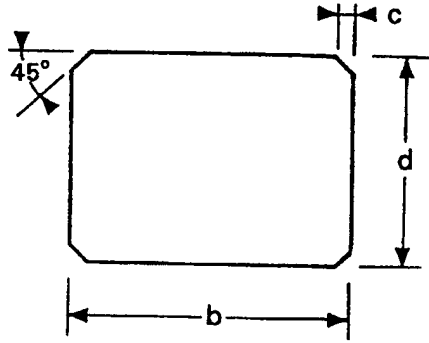

**Figure 1. Specimen Cross Section for a Chamfered-Edge Beam.**

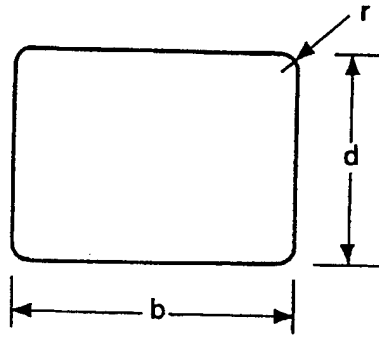

**Figure 2. Specimen Cross Section for a Rounded-Edge Beam.**

$$I_t = \frac{b(d-2r)^3}{12} + \frac{(b-2r)r^3}{6} + \frac{(b-2r)(d-r)^2 r}{2} + 4r^4 \left( \frac{\pi}{16} - \frac{4}{9\pi} \right) + \pi r^2 \left[ \frac{d}{2} - r \left( 1 - \frac{4}{3\pi} \right) \right]^2. \quad (9)$$

Combining equations 2 and 3, the true elastic modulus,  $E_{cor}$ , may be calculated as follows:

$$\frac{E_{cor}}{E_b} = \frac{C_{1,cor} W f^2}{C_{1,b} W f^2} = \frac{I_b}{I_t}, \quad (10)$$

where  $E_b$  and  $C_{1,b}$  are the calculated elastic modulus (using either equation 4 or 6) and constant  $C_1$ , respectively (assuming the specimen is a simple rectangular beam), uncorrected for chamfers

or edge rounding.  $C_{1,cor}$  is the  $C_1$  term corrected for the chamfering or edge rounding. The weight and frequency,  $f$ , are the values measured for the chamfered or edge-rounded beam. Then

$$E_{cor} = \left( \frac{I_b}{I_t} \right) E_b. \quad (11)$$

For standard specimens with a 3-mm  $\times$  4-mm cross section size,\*

$$E_{cor} = FE_b, \quad (12)$$

where  $F^\dagger$  is the correction factor for the change in  $I$  that is due to the edge treatment and is given in Table 1 for various chamfers. Analogous values of  $F^\dagger$  for the same standard specimens with rounded edges of radius  $r$  are given in Table 2.

Equations 11 and 12, with moment of inertia correction only, should be used with equation 4 when the true density is known. The latter may be obtained from a water displacement measurement, or calculated from the mass and volume of the beam provided that the correction is made for the reduction in volume due to the edge treatment.

On the other hand, many standard test methods use equation 6, for which an assumption regarding the density, mass, and physical dimensions of the specimen (equation 5) has been invoked. If an edge treated beam is used, then an additional correction to remedy this assumption should be made as follows. The correct density,  $\rho_T$ , of a chamfered beam is

$$\rho_T = m/\ell(bd - 2c^2), \quad (13)$$

---

\* The same factor may be applied to correct the flexure stress,  $\sigma_t = F\sigma_b$ , where  $\sigma_t$  is the true, maximum flexure stress in a chamfered or rounded beam and  $\sigma_b$  is the apparent flexure stress assuming a rectangular cross section.

<sup>†</sup>The adjustments listed in Tables 1 and 2 are applicable only for flexural modes of resonance and are not appropriate for the longitudinal or torsional resonance modes.

**Table 1. Correction Factors, F and P, for Chamfered Standard 3-mm × 4-mm Strength Test Specimens<sup>a</sup>**

c (mm)	Moment Correction Factor, F b = 4 mm, d = 3 mm	Density Correction Factor, P b = 4 mm, d = 3 mm
0.080	1.0031	1.0011
0.090	1.0039	1.0014
0.100	1.0048	1.0017
0.110	1.0058	1.0020
0.115	1.0063	1.0022
0.118	1.0066	1.0023
0.120	1.0069	1.0024
0.122	1.0071	1.0025
0.124	1.0073	1.0026
0.126	1.0076	1.0027
0.128	1.0078	1.0027
0.130	1.0080	1.0028
0.132	1.0083	1.0029
0.134	1.0085	1.0030
0.136	1.0088	1.0031
0.138	1.0090	1.0032
0.140	1.0093	1.0033
0.150	1.0106	1.0038
0.160	1.0121	1.0043
0.170	1.0136	1.0048
0.180	1.0152	1.0054
0.190	1.0169	1.0061
0.200	1.0186	1.0067
0.210	1.0205	1.0074
0.220	1.0224	1.0081
0.230	1.0244	1.0089
0.240	1.0265	1.0097
0.250	1.0287	1.0105

<sup>a</sup> A chamfer size of 0.150 mm is the maximum value allowed for this geometry by ASTM C1161 and ISO 17404.

**Table 2. Correction Factors, F and P, for Edge Rounded Standard 3-mm × 4-mm Strength Test Specimens<sup>a</sup>**

r (mm)	Moment Correction Factor, F b = 4 mm, d = 3 mm	Density Correction Factor, P b = 4 mm, d = 3 mm
0.080	1.0013	1.0005
0.090	1.0017	1.0006
0.100	1.0021	1.0007
0.110	1.0025	1.0009
0.120	1.0030	1.0010
0.130	1.0035	1.0012
0.140	1.0041	1.0014
0.150	1.0046	1.0016
0.160	1.0053	1.0018
0.170	1.0059	1.0021
0.180	1.0066	1.0023
0.190	1.0074	1.0026
0.200	1.0082	1.0029
0.210	1.0090	1.0032
0.220	1.0098	1.0035
0.230	1.0107	1.0038
0.240	1.0116	1.0041
0.250	1.0126	1.0045
0.260	1.0136	1.0049
0.270	1.0146	1.0052
0.280	1.0157	1.0056
0.290	1.0168	1.0061
0.300	1.0180	1.0065

<sup>a</sup> A rounded edge of 0.200 mm is the maximum value allowed for this geometry by ASTM C1161 and ISO 14704.

and for an edge rounded beam,

$$\rho_T = m/\ell(bd - r^2(4 - \pi)), \quad (14)$$

and then

$$E_{cor} = \left( \frac{I_b}{I_t} \right) \left( \frac{\rho_T}{\rho_b} \right) E_{b,m}, \quad (15)$$

where  $E_{b,m}$  is from equation 6, which assumes the beam is an ideal rectangle. For standard 3-mm  $\times$  4-mm cross section specimens, the corrected modulus is

$$E_{cor} = FPE_{b,m}, \quad (16)$$

where  $P$  is the correction factor for the change in  $\rho$  due to the edge treatment. Values of  $P$  for standard 3-mm  $\times$  4-mm specimens with either chamfered or rounded edges are listed in Tables 1 and 2, respectively.

## 2. Experimental Procedure

Four ceramic materials listed in Table 3 were used to examine the effect of edge chamfering on the resonant frequency. Rectangular specimens were prepared with a chamfer geometry as depicted in Figure 1. Three of the four materials had average chamfer sizes (Table 3), which are well over the 0.15-mm tolerance commonly specified in flexure strength standards. The resonant frequency of each material was measured with a commercial impulse excitation instrument.\* The resonant frequency typically was measured three to five times for each specimen and was repeatable to within 0.01 kHz. The specimen cross section dimensions were measured with a hand micrometer with a resolution and precision of 0.002 mm. Some specimens may have had a slight thickness taper ( $\sim 0.002$  mm) along the length, so the cross section dimensions were measured in the middle of the beam. Length was measured with a hand caliper with a resolution of 0.01 mm. Mass was measured with a precision laboratory balance to within 0.001 g, and the density was determined using the mass and physical dimensions of the specimen. The elastic modulus was calculated using equation 4. For a perfectly rectangular beam, the uncertainty of the elastic modulus may be estimated from a propagation of uncertainties of the individual variables in equation 4 [20]. Using the instrument resolutions and precisions listed previously, the type B (95% confidence limit) uncertainties for mass, width, thickness, length, and frequency

---

\* Grindosonic Mk5, J. W. Lemmens, Inc., St. Louis, MO.

**Table 3.  $E_{b,m}$  and  $E_{cor}$  Values for Ceramic Materials**

Material <sup>a</sup>	Density ( $\rho_r$ ) <sup>f</sup> (g/cm <sup>3</sup> )	Average Frequency (kHz)	Average $E_{b,m}$ (GPa)	Average c (mm)	Moment (I) Correction Factor (F)	$E_{cor}$ [I Only] (GPa)	Density ( $\rho$ ) Correction Factor (P)	$E_{cor}$ [ $\rho$ and I] (GPa)
sintered Al <sub>2</sub> O <sub>3</sub> <sup>b</sup>	3.956 ± 0.003	11.02	384.2 ± 0.6	0.230	1.0258 <sup>g</sup>	394.1 ± 0.6	1.0095	397.8 ± 0.6
hot-pressed SiC <sup>c</sup>	3.206 ± 0.003	14.29	445.9 ± 1.4	0.191	1.0170	453.5 ± 1.5	1.0061	456.2 ± 1.5
hot-pressed TiB <sub>2</sub> <sup>d</sup>	4.392 ± 0.008	12.83	488.4 ± 3.6	0.132	1.0083	492.5 ± 3.8	1.0029	493.9 ± 3.6
AlON <sup>e</sup>	3.644 ± 0.006	11.65	312.0 ± 1.6	0.198	1.0183	317.7 ± 1.4	1.0066	319.8 ± 1.4

<sup>a</sup> Certain commercial materials or equipment are identified in this report to adequately specify the experimental procedure. Such identification does not imply endorsement by the National Institute of Standards and Technology or the U.S. Army Research Laboratory nor does it imply that these materials or equipment are necessarily the best for the purpose.

<sup>b</sup> Grade AD-999, Coors, Golden, CO.

<sup>c</sup> Grade SiC-N, Cercom Inc., Vista, CA.

<sup>d</sup> Cercom Inc., Vista, CA.

<sup>e</sup> Raytran Aluminum Oxynitride, Raytheon Company, Lexington, MA.

<sup>f</sup> Calculated from mass and physical dimensions of unchamfered specimens, or in the case of alumina, from chamfered specimens with correction.

<sup>g</sup> Since the alumina specimens did not have 3-mm × 4-mm cross sections, F was obtained using equations 8 and 11 and not from Table 1.

Notes: Uncertainties are ±1 standard deviation based upon scatter of the individual outcomes from 3–5 specimens per material.



are 0.042%, 0.050%, 0.067%, 0.020%, and 0.091%, respectively. The total uncertainty in  $E$  is 0.29%. The chamfer sizes were measured with a binocular stereomicroscope at magnifications of up to 160 $\times$  in conjunction with a precision traversing stage with micrometer heads with a digital readout of 0.001-mm resolution. All four chamfers were measured. There was some variability in chamfer sizes for a given specimen, but only an average value for each specimen was used for the purpose of correcting the elastic modulus.

### 3. Results and Discussion

Table 3 summarizes the measured (uncorrected) elastic modulus,  $E_b$ , values determined from these frequencies and the elastic modulus values corrected for density and the edge chamfering,  $E_{cor}$ .

Three sintered alumina specimens were 2.816 mm  $\times$  4.006 mm  $\times$  50.7 mm in size, close to the standard size of 3 mm  $\times$  4 mm  $\times$  45 mm – 50 mm. The resonant frequencies of the three bars were nearly identical: 10.99 kHz, 11.06 kHz, and 11.00 kHz. The uncorrected elastic moduli averaged 384.2 GPa. This was corrected, for I only, by 2.58% for the finite chamfer size of 0.230 mm to 394.1 GPa, a value in excellent agreement with 395 GPa measured by an ultrasonic time-of-flight method on the same batch of material as shown in Table 4. (Since the alumina specimens did not have standard 3-mm  $\times$  4-mm cross sections, the moment correction factor,  $F$ , was obtained using equations 8 and 11, and not from Table 1.) The correction for the true density increased  $E_{cor}$  by an additional 0.95% to 397.8 GPa. This value is good in agreement with the ultrasonic time of flight value. A single additional chamfered specimen was strain gauged and tested in a semiarticulating four-point flexure fixture. The static elastic modulus calculated from the static strains was 386.9 GPa, which is slightly higher than the uncorrected dynamic  $E$  but lower than the correct dynamic  $E$ . Static elastic modulus and strain gauge uncertainties may be of the order of several percent [4, 21], which may account for the discrepancy between the static and dynamic  $E$  values.

**Table 4. Comparison of Corrected Beam Resonance Elastic Moduli,  $E_{cor}$ , to Values From Other Methods**

Material	E resonance, chamfered, [corrected for I only] (GPa)	E resonance, chamfered, [corrected for I and P] (GPa)	E resonance, unchamfered (GPa)	E ultrasonic, time of flight (GPa)	E resonance disks (GPa)
sintered $Al_2O_3$	394.1	397.8	—	395	—
hot-pressed SiC	453.5	456.2	453.5	—	—
hot-pressed $TiB_2$	492.5	493.3	491.9	—	—
AlON	317.7	319.8	317.7	—	316.7

Notes: — = Not measured.

Flexure specimens of the three other ceramic materials were prepared, both with and without edge chamfering. Most of the bars had nominal dimensions of 3 mm × 4 mm × 50 mm, with the sole exception of the SiC specimens without edge chamfering, which were slightly larger, having nominal dimension of 3.8 mm × 4 mm × 51 mm. Ten specimens, 5 with chamfering and 5 without, were examined for each of the  $TiB_2$  and AlON materials, while 8 specimens, 4 with chamfering and 4 without, were examined for the SiC.

The average resonant frequencies measured for the SiC,  $TiB_2$  and AlON, with chamfers resulted in uncorrected average elastic moduli values,  $E_b$ , of 445.9 GPa, 488.4 GPa, and 312.0 GPa, respectively. These values were then corrected, for I only, by 1.70%, 0.83%, and 1.83%, respectively, based on the average chamfer sizes, which ranged from 0.13 mm to 0.20 mm (Table 3). The corrected values compare exceptionally well with computed elastic moduli for specimens *without chamfers*, as shown in Table 4. As in the alumina instance, the second correction for the true density increased  $E_{cor}$  for all three of these material. When compared to the results from the unchamfered bars and the other methods, these values are still in good agreement, but they do not agree as well as the values corrected for I only.

In the case of the AlON, comparable resonance values were available from testing 10 disks, nominally 50 mm in diameter × 8.3 mm thick, determined in accordance with ASTM C 1259 [11]. The average elastic modulus was 316.7 GPa, in excellent agreement with the beam resonance results (Table 4) from unchamfered bars and from chamfered bars corrected for I only.

## 4. Summary

In summary, the mathematical solutions to account for the effect of edge chamfers on the density and moment of inertia, and in turn the dynamic elastic modulus, of a rectangular ceramic beam has been experimentally verified. The analysis and experimental results show that change in the moment of inertia, due to edge chamfering, has a greater impact on the resultant elastic modulus of a rectangular ceramic beam than the change in density. For standard 3 mm  $\times$  4 mm cross section beams Tables 1 and 2 provide a simple means to correct elastic moduli values for the change in moment of inertia and density due to edge chamfering or rounding. For beams with nonstandard cross sections, equation 11 or 15 should be used, depending on the type of edge treatment and whether the true density is available.

## 5. References

1. Spinner, S., and W. E. Tefft. "A Method for Determining Mechanical Resonance Frequencies and for Calculating Elastic Moduli from These Frequencies." *Proceedings of the American Society for Testing and Materials*, pp. 1221-1238, 1961.
2. Spinner, S., T. W. Reichard, and W. E. Tefft. "A Comparison of Experimental and Theoretical Relations Between Young's Modulus and the Flexural and Longitudinal Resonance Frequencies of Uniform Bars." *Journal of Research of the National Bureau of Standards, A, Physics and Chemistry*, vol. 64A, no. 2, pp. 147-155, 1960.
3. Pickett, G. "Equations for Computing Elastic Constants From Flexural and Torsional Resonant Frequencies of Vibration of Prisms and Cylinders." *Proceedings of the American Society for Testing and Materials*, vol. 45, pp. 846-865, 1945.
4. Dickson, R. W., and J. B. Wachtman. "An Alumina Standard Reference Material for Resonance Frequency and Dynamic Elastic Moduli Measurement, I For Use at 25°C." *Journal of Research of the National Bureau of Standards, A, Physics and Chemistry*, vol. 75A, no. 3, pp. 155-162, 1971.
5. Smith, J. S., M. Wyrick, and J. M. Poole. "An Evaluation of Three Techniques for Determining the Young's Modulus of Mechanically Alloyed Materials." *Dynamic Elastic Modulus Measurements in Materials, STP 1045*, edited by A. Wolfenden, ASTM, West Conshohocken, PA, pp. 195-207, 1990.
6. Forster, F. "New Method for Determination of Modulus of Elasticity and Damping." *Zeitschrift fur Metallkunde*, vol. 29, pp. 109-115, 1937.
7. Goens, E. "Über die Bestimmung des Elastizitätsmodulus von Stäben mit Hilfe von Biegungsschwingungen." *Annals of Physics, B (Series)*, vol. 11, pp. 649-678, 1931.
8. Timoshenko, S. P. "On the Transverse Vibrations of Bars of Uniform Cross Section." *Philosophical Magazine, Series 6*, vol. 43, pp. 125-131, 1922.
9. American Society for Testing and Materials. "Standard Test Method for Dynamic Young's Modulus, Shear Modulus, and Poisson's Ratio for Advanced Ceramics by Sonic Resonance." C 1198-96, *Ann. Book of Stds.*, vol. 15.01, West Conshohocken, PA, 1999.
10. American Society for Testing and Materials. "Standard Test Method for Dynamic Young's Modulus, Shear Modulus, and Poisson's Ratio by Sonic Resonance," C 1875-98, *Ann. Book of Stds.*, vol. 3.01, West Conshohocken, PA, 1999.

11. American Society for Testing and Materials. "Standard Test Method for Dynamic Young's Modulus, Shear Modulus, and Poisson's Ratio in Advanced Ceramics by Impulse Excitation of Vibration." C 1259-96, *Ann. Book of Stds.*, vol. 15.01, West Conshohocken, PA, 1999.
12. American Society for Testing and Materials. "Standard Test Method for Dynamic Young's Modulus, Shear Modulus, and Poisson's Ratio by Impulse Excitation of Vibration." C 1876-98, *Ann. Book of Stds.*, vol. 3.01, West Conshohocken, PA, 1999.
13. American Society for Testing and Materials. "Standard Test Method for Young's Modulus, Shear Modulus, and Poisson's Ratio for Glass and Glass-Ceramics by Resonance." C 623-95, *Ann. Book of Stds.*, vol. 15.02, 1999.
14. American Society for Testing and Materials. "Standard Test Method for Young's Modulus, Shear Modulus, and Poisson's Ratio for Glass and Glass-Ceramics by Resonance." C 848-88, *Ann. Book of Stds.*, vol. 15.02, 1999.
15. Baratta, F. "Requirements for Flexure Testing of Brittle Materials." U.S. Army TR 82-20, U.S. Army Materials and Mechanics Research Center, Watertown, MA, April 1982.
16. Baratta, F., G. Quinn, and W. Matthews. "Errors Associated With Flexure Testing of Brittle Materials." U.S. Army MTL-TR 87-35, U.S. Army Materials Technology Laboratory, Watertown, MA, July 1987.
17. Duckworth, W. H. "Precise Tensile Properties of Ceramic Bodies." *Journal of the American Ceramic Society*, vol. 34, no. 1, pp. 1-9, 1951.
18. American Society for Testing and Materials. "Standard Test Method for Flexural Strength of Advanced Ceramics at Ambient Temperatures." C1161-94, *Ann. Book of Stds.*, vol. 15.01, West Conshohocken, PA, 1999.
19. International Standards Organization. "Standard Test Method for Flexural Strength of Monolithic Ceramics at Room Temperature." ISO/DIS 14704, Technical Committee TC 206 Draft International Standard, Geneva, Switzerland, 1999.
20. Schenck, H., Jr. *Theories of Engineering Experimentation*. Second edition, New York: McGraw Hill, 1968.
21. Pople, J. "Errors and Uncertainties in Strain Measurements." *Strain Gage Technology*, Elsevier England: Applied Sciences, 2nd ed., edited by A. L. Windrow, pp. 217-274, 1989.

NO. OF  
COPIES   ORGANIZATION

2   DEFENSE TECHNICAL  
INFORMATION CENTER  
DTIC DDA  
8725 JOHN J KINGMAN RD  
STE 0944  
FT BELVOIR VA 22060-6218

1   HQDA  
DAMO FDT  
400 ARMY PENTAGON  
WASHINGTON DC 20310-0460

1   OSD  
OUSD(A&T)/ODDDR&E(R)  
R J TREW  
THE PENTAGON  
WASHINGTON DC 20301-7100

1   DPTY CG FOR RDA  
US ARMY MATERIEL CMD  
AMCRDA  
5001 EISENHOWER AVE  
ALEXANDRIA VA 22333-0001

1   INST FOR ADVNCD TCHNLGY  
THE UNIV OF TEXAS AT AUSTIN  
PO BOX 202797  
AUSTIN TX 78720-2797

1   DARPA  
B KASPAR  
3701 N FAIRFAX DR  
ARLINGTON VA 22203-1714

1   NAVAL SURFACE WARFARE CTR  
CODE B07 J PENNELLA  
17320 DAHLGREN RD  
BLDG 1470 RM 1101  
DAHLGREN VA 22448-5100

1   US MILITARY ACADEMY  
MATH SCI CTR OF EXCELLENCE  
DEPT OF MATHEMATICAL SCI  
MADN MATH  
THAYER HALL  
WEST POINT NY 10996-1786

NO. OF  
COPIES   ORGANIZATION

1   DIRECTOR  
US ARMY RESEARCH LAB  
AMSRL D  
D R SMITH  
2800 POWDER MILL RD  
ADELPHI MD 20783-1197

1   DIRECTOR  
US ARMY RESEARCH LAB  
AMSRL DD  
2800 POWDER MILL RD  
ADELPHI MD 20783-1197

1   DIRECTOR  
US ARMY RESEARCH LAB  
AMSRL CS AS (RECORDS MGMT)  
2800 POWDER MILL RD  
ADELPHI MD 20783-1145

3   DIRECTOR  
US ARMY RESEARCH LAB  
AMSRL CI LL  
2800 POWDER MILL RD  
ADELPHI MD 20783-1145

ABERDEEN PROVING GROUND

4   DIR USARL  
AMSRL CI LP (BLDG 305)

NO. OF  
COPIES ORGANIZATION

1 J W LEMMENS INC  
A V LEUVEN  
3466 BRIDGELAND DR  
ST LOUIS MO 63044-2606

1 GATEWAY MATERIALS  
TECHNOLOGY INC  
S T GONCZY  
221 S EMERSON  
MT PROSPECT IL 60056

1 NASA GLEN RESEARCH CTR  
J SALEM MS 49 7  
21000 BROOKPARK RD  
CLEVELAND OH 44135

5 NIST  
G QUINN  
BLDG 223 RM A329  
CERAMICS DIV  
GAITHERSBURG MD 20899

ABERDEEN PROVING GROUND

13 DIR USARL  
AMSRL WM MC  
J J SWAB (10)  
J LASALVIA  
P PATEL  
G GILDE

**NO. OF  
COPIES ORGANIZATION**

- |   |   |
|---|---|
| 1 | NATIONAL PHYSICAL LAB<br>R MORRELL<br>BLDG 13<br>QUEENS RD<br>TEDDINGTON MIDDLESEX<br>TW11 OLW<br>UNITED KINGDOM                      |
| 1 | NATIONAL RESEARCH INSTITUTE<br>OF NAGOYA<br>CERAMIC SCIENCE DEPT<br>S SAKAGUCHI<br>1-1 HIRATE-CHO KITA-KU<br>NAGOYA 462-8510<br>JAPAN |



INTENTIONALLY LEFT BLANK.

REPORT DOCUMENTATION PAGE			Form Approved OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project(0704-0188), Washington, DC 20503.				
1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE July 2000		3. REPORT TYPE AND DATES COVERED Final, 1999
4. TITLE AND SUBTITLE Elastic Modulus by Resonance of Rectangular Prisms: Corrections for Edge Treatments			5. FUNDING NUMBERS 982S31	
6. AUTHOR(S) George D. Quinn* and Jeffrey J. Swab				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) U.S. Army Research Laboratory ATTN: AMSRL-WM-MC Aberdeen Proving Ground, MD 21005-5069			8. PERFORMING ORGANIZATION REPORT NUMBER ARL-TN-165	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)			10. SPONSORING/MONITORING AGENCY REPORT NUMBER	
11. SUPPLEMENTARY NOTES *National Institute of Standards and Technology, Ceramics Division, Gaithersburg, MD 20899				
12a. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution is unlimited.			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) The dynamic elastic moduli of isotropic, homogeneous ceramics is commonly determined by resonance methods. A prismatic beam specimen is vibrated in a flexural mode, and the resonant frequency is measured. The beam may have a square, rectangular, or circular cross section. Elastic modulus is determined from the resonant frequency, the mass or density of the prism, and the beam's physical dimensions. Under ideal circumstances, the beam cross section should have a simple prismatic shape, but in practice, the method is sometimes applied to rectangular specimens with edge chamfers or radii that are applied to reduce edge flaw sensitivity during strength tests. The effect of such edge treatments on the resonance frequency and a simple means to correct the calculated elastic modulus for the edge treatment are provided in this note.				
14. SUBJECT TERMS elastic modulus, resonant frequency, edge treatments			15. NUMBER OF PAGES 22	
			16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT UNCLASSIFIED	18. SECURITY CLASSIFICATION OF THIS PAGE UNCLASSIFIED	19. SECURITY CLASSIFICATION OF ABSTRACT UNCLASSIFIED	20. LIMITATION OF ABSTRACT UL	

INTENTIONALLY LEFT BLANK.

## USER EVALUATION SHEET/CHANGE OF ADDRESS

This Laboratory undertakes a continuing effort to improve the quality of the reports it publishes. Your comments/answers to the items/questions below will aid us in our efforts.

1. ARL Report Number/Author ARL-TN-165 (Swab) Date of Report July 2000

2. Date Report Received \_\_\_\_\_

3. Does this report satisfy a need? (Comment on purpose, related project, or other area of interest for which the report will be used.) \_\_\_\_\_

4. Specifically, how is the report being used? (Information source, design data, procedure, source of ideas, etc.) \_\_\_\_\_

5. Has the information in this report led to any quantitative savings as far as man-hours or dollars saved, operating costs avoided, or efficiencies achieved, etc? If so, please elaborate. \_\_\_\_\_

6. General Comments. What do you think should be changed to improve future reports? (Indicate changes to organization, technical content, format, etc.) \_\_\_\_\_

CURRENT  
ADDRESS

Organization

Name

E-mail Name

Street or P.O. Box No.

City, State, Zip Code

7. If indicating a Change of Address or Address Correction, please provide the Current or Correct address above and the Old or Incorrect address below.

OLD  
ADDRESS

Organization

Name

Street or P.O. Box No.

City, State, Zip Code

(Remove this sheet, fold as indicated, tape closed, and mail.)  
(DO NOT STAPLE)